

Morin-type transition in 5C pyrrhotite

CHARLES R.S. HAINES^{1,*}, GIULIO I. LAMPRONTI¹, WIM T. KLOOSTER², SIMON J. COLES²,
SIÂN E. DUTTON³, AND MICHAEL A. CARPENTER¹

¹Department of Earth Sciences, University of Cambridge, Cambridge, U.K.

²U.K. National Crystallographic Service, Chemistry, Faculty of Natural and Environmental Sciences, University of Southampton, SO17 1BJ, U.K.

³Department of Physics, University of Cambridge, Cambridge, U.K.

ABSTRACT

We report the discovery of a low-temperature spin-flop transition in 5C pyrrhotite at ~155 K that is similar to those seen in hematite at 260 K and FeS (troilite) at 440 K. The 5C crystal was produced by annealing a 4C pyrrhotite crystal at 875 K to produce a change in the vacancy-ordering scheme that developed during cooling. The 5C structure is confirmed by single-crystal X-ray diffraction and the stoichiometry and homogeneity by electron microprobe and SEM BSE mapping. Resonant ultrasound spectroscopy (RUS), heat capacity, and magnetization measurements from room temperature down to 2 K are reported. The transition is marked by a steep change in elastic properties at the transition temperature, a peak in the heat capacity, and weak anomalies in measurements of magnetization. Magnetic hysteresis loops and comparison with the magnetic properties of 4C pyrrhotite suggest that the transition involves a change in orientation of moments between two different antiferromagnetic structures, perpendicular to the crystallographic *c*-axis at high temperatures and parallel to the crystallographic *c*-axis at low temperatures. The proposed structures are consistent with a group theoretical treatment that also predicts a first-order transition between the magnetic structures.

Keywords: Pyrrhotite, palaeomagnetism, mineralogy, crystal structure

INTRODUCTION

The pyrrhotite system comprises several related structures having compositions Fe_{1-x}S where $0 < x < 0.125$. The best known of these structures are troilite (FeS) and 4C pyrrhotite (Fe_7S_8). 4C is so called because it is a superstructure with a 4 cell repeat along the *c*-axis with respect to the parent NiAs structure (Bertaut 1953; Powell et al. 2004). Other commensurate superstructures have been reported as 3C (Fleet 1971; Nakano et al. 1979), 5C (de Villiers et al. 2009; Elliot 2010; Liles and De Villiers 2012), and 6C (Koto et al. 1975; de Villiers and Liles 2010), while some are incommensurate (Nakazawa and Morimoto 1971; Morimoto et al. 1975; Yamamoto and Nakazawa 1982; Izaola et al. 2007). Ferrimagnetic pyrrhotite (4C) is an important carrier of magnetic remanence on earth and possibly also on Mars (e.g., Rochette et al. 2005; Martín-Hernández et al. 2008), but 4C structures are not unique, and the other superstructure types have different structure/property relationships that are much less well known. The key issue in relation to the magnetic structures is how vacancies order on the cation sites as the stoichiometry changes and how the distribution of vacancies then controls the magnetic structures.

By adopting a group theoretical approach, Haines et al. (2019) have shown that the commensurate superstructures of pyrrhotite, which have different Fe/vacancy ordering schemes, are all likely to undergo a magnetically driven spin reorientation transition with accompanying small distortions of the crystal lattice at low temperatures. The prediction for the case of 5C pyrrhotite is for

an abrupt spin-flop transition similar to the Morin transition in hematite. The present work focuses on the magnetic and elastic properties of a natural 4C crystal that transformed unexpectedly to 5C crystal after being heated above its concomitant vacancy ordering and Néel temperature of 595 K. We report a newly identified magnetic transition at ~155 K in the 5C crystal and propose that it is a spin-flop transition between two antiferromagnetic structures, with an origin that is closely related to that of the magnetic transition already known in FeS at 440 K.

In general, 5C pyrrhotite is found to have a composition close to Fe_9S_{10} . However, Pósfai et al. (2000) reported a 5C polytype with composition Fe_7S_8 . Kontny et al. (2000) also presented some X-ray diffraction and magnetization measurements on multiphase samples, suggesting the possibility of pyrrhotite with a 5C structure having the stoichiometry close to the Fe_7S_8 that is usually associated with the 4C structure. de Villiers et al. (2009) proposed space group *Cmce* (no. 63, formerly *Cmca*) as the correct crystallographic space group at room temperature. Elliot (2010) had claimed $P2_1/c$ for the room-temperature structure. Liles and De Villiers (2012) subsequently proposed $P2_1$ for the structure at both room temperature and 120 K. There do not appear to have been any studies of the magnetic structure.

In this work, we first establish the stoichiometry of the sample through electron microprobe analysis before going on to present a structural solution in the space group *Cmce* based on single-crystal X-ray diffraction data collected on a single-crystal sample of 5C pyrrhotite at room temperature. We then present heat capacity, DC magnetization, and resonant ultrasound spectroscopy (RUS) measurements on a second single crystal over the range 2–300 K.

* E-mail: crsh2@cam.ac.uk. ORCID 0000-0002-1274-8329.

SAMPLE PREPARATION

The single-crystal sample of pyrrhotite used in this study was cut from a centimeter-sized crystal in the mineral collection of the South Australia Museum that had originated from a mine in Mexico. Samples from the same parent crystal have been described in Haines et al. (2020a). At the start, it was nearly in the shape of a rectangular parallelepiped with two pairs of parallel faces 1.7 and 1.5 mm apart and a third pair of non-parallel faces separated by between 1 and 1.5 mm. The first experiment was to collect RUS spectra through the temperature interval 10–295 K to confirm that it was 4C pyrrhotite with a Besnus transition (Besnus and Meyer 1964) at ~35 K (Haines et al. 2020b).

After removal from the RUS instrument, the crystal was heated slowly to 875 K in flowing argon, with an oxygen trap, over four and a half days before cooling it back to room temperature over three days. The sample was held between two alumina rods. The heating and cooling rates through the 595 K transition were 2.2 K/h. As a consequence of this treatment, the crystal acquired a thin oxide layer that was removed mechanically and also broke into two pieces. The larger piece had a mass of 9.1 ± 0.1 mg and was used for heat capacity, magnetization, and RUS measurements. On completion of these measurements, the larger piece was mounted and polished for chemical analysis. The smaller piece weighed 2.2 ± 0.1 mg and was broken up for the single-crystal X-ray diffraction measurements.

ELECTRON MICROPROBE ANALYSIS

Chemical analysis on the larger piece was carried out using a Cameca SX100 electron microprobe in the Department of Earth Sciences, University of Cambridge (instrumental conditions: 20 keV, 10 nA, 1 μ m beam diameter). With respect to 10 sulfur atoms, the average of 20 analyses gave the number of Fe atoms as 9.21 ± 0.05 . Co, Cu, Mn, Ni, and Zn were measured for, but all were below the detection limit on all of the 20 analysis spots. We highlight here that this shows a significant change in stoichiometry from the parent crystal described in Haines et al. (2020a) in which electron microprobe analysis revealed a homogeneous and pure 4C crystal of stoichiometry $7.00(6)$ Fe atoms per 8 sulfur atoms. We suggest that this change of stoichiometry is due to the loss of sulfur from the crystal rather than the addition of iron for which no source or mechanism is present. To check for zoning or inhomogeneity in the stoichiometry of the crystal a scanning electron microscope backscattered electron (SEM-BSE) analysis map of nearly the whole surface of the same piece used for the electron microprobe analysis was collected. The SEM-BSE map showed no sign of any chemical inhomogeneity above the level of detection. We therefore conclude that the transformation from stoichiometry $\text{Fe}_{7.00(6)}\text{S}_8$ to $\text{Fe}_{9.21(5)}\text{S}_{10}$ is complete and homogeneous. The images are included as supplemental information¹ (SI 2020).

SINGLE-CRYSTAL X-RAY DIFFRACTION

The single crystal used for X-ray diffraction was black and plate-shaped, with dimensions $\sim 0.080 \times 0.040 \times 0.020$ mm³. It was mounted on a MITIGEN holder in perfluoropolyether oil on a Rigaku FRE+ diffractometer equipped with VHF Varimax confocal mirrors and an AFC12 goniometer and HyPix 6000HE detector. The temperature was 293 ± 2 K during scans of 0.5°

per frame for 1.3 s with Mo K radiation (rotating-anode X-ray tube, 40 kV, 30 mA). The total number of runs and images was based on the strategy calculation from the program CrysAlisPro (Rigaku, V1.171.39.46, 2018). The maximum resolution achieved was at 27.478° ($0.77 \text{ \AA}$). Cell parameters were retrieved using the CrysAlisPro (Rigaku, V1.171.39.46, 2018) software and refined using CrysAlisPro (Rigaku, V1.171.39.46, 2018) on 5787 reflections, 22% of the observed reflections. Data reduction, scaling, and absorption corrections were performed using CrysAlisPro (Rigaku, V1.171.39.46, 2018). The final completeness is 99.7% out to 25° in Θ . A multi-scan absorption correction was performed using CrysAlisPro 1.171.39.46 (Rigaku Oxford Diffraction 2018) using spherical harmonics as implemented in SCALE3 ABSPACK. The absorption coefficient of this material is 13.664 mm^{-1} at this wavelength ($= 0.711 \text{ \AA}$), and the minimum and maximum transmissions are 0.522 and 1.000, respectively.

Figure 1 shows a section of the $(0kl)$ plane of the diffraction pattern, with five superlattice reflections clearly visible along the $c^*(k_z)$ of the parent NiAs cell. We looked for evidence of incommensuration by initially indexing the pattern with the NiAs unit cell and then using an incommensurate k -vector to describe the remaining peaks. The k -vector that describes the pattern has components of $0.500(3)$ along the planar hexagonal axes and $0.204(6)$ perpendicular to the ab -plane of the parent structure. This is, therefore, commensurate within experimental uncertainty.

The structural solution and subsequent refinement were undertaken using the SHELXS program (Sheldrick 1997), proceeding with 9 Fe and 8 S atomic positions. Neutral scattering factors were used for all atoms. The appropriate 3-individual twin matrix describing a 120° rotation along the c axis was introduced in the first stages of the refinement; since the three individual fractions were found to be all close to 33%, this step was necessary to take the discrepancy factor $R1$ below 0.2. Individual occupancy factors for the Fe atoms were refined with an overall isotropic thermal parameter to detect the partially vacant sites. The Fe sites that refined to occupancies close to 1.0 were then fixed at

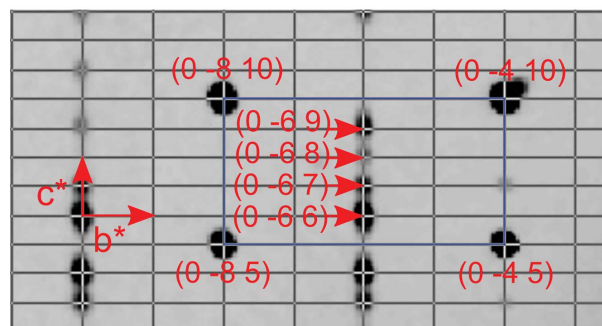


FIGURE 1. Part of the $(0kl)$ precession image of the room-temperature single-crystal X-ray diffraction pattern, showing the fivefold superlattice reflections of the 5C structure. The data has been reduced using the cell from the $Cmce$ structure and the peaks are labeled with the (hkl) of the $Cmce$ structure. The direction of b^* and c^* are given in red on the left. The unit cell of the $Cmce$ structure is shown by the gray grid. The projection of the hexagonal parent cell onto the $Cmce$ $(0kl)$ plane is shown in blue. The fivefold modulation in the l direction can be seen and the peaks characteristic of this are labeled with their (hkl) values. (Color online.)

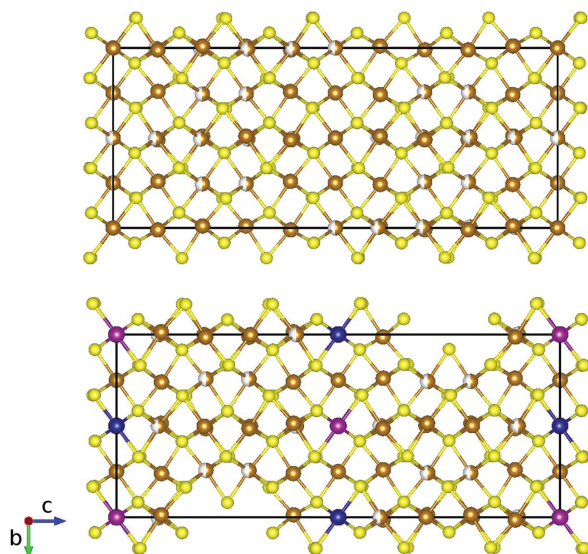


FIGURE 2. Structural model of pyrrhotite 5C viewed along [100] from this work (top) and from de Villiers et al. (2009) (bottom). Color code: yellow = S; brown = Fe (partial occupancy is shown by half-gray half-brown); pink = partially Ni replaced Fe site (de Villiers et al. 2009); blue = vacant metal site from de Villiers et al. (2009) (see main text for details). (Color online.)

unity, and the thermal displacement parameters were then refined independently. Last, the ADPs were refined anisotropically, together with the occupancies of the four partially vacant Fe atoms. Because of an unreasonably prolate ADP for the atom at (0,0,0) Fe9 the thermal displacement parameters were restrained to be similar to those of the neighbor Fe sites. We here highlight that this is not the same position found to be vacant in the structural refinement performed by de Villiers et al. (2009), corresponding

to Fe4 in our model. Details of the structural solutions are given in the accompanying cif¹.

The refinement converged with a discrepancy factor $R1 = 0.0485$ for 1675 observed reflections and $R1 = 0.0604$ for all 2084 measured reflections and 120 parameters. The goodness of fit parameter was $S = 1.476$ and $wR2$ was 0.3431. No extinction correction parameter was used as it was found to converge to zero. The largest residual electron density amounted to $1.32 \text{ e}/\text{\AA}^3$. Interestingly, the structural model reported by de Villiers et al. (2009) also differs in the way the Fe planes stack along the [001] direction (see Fig. 2).

The composition, calculated from the refinement of the structure, is $\text{Fe}_{9.22(1)}\text{S}_{10}$, in excellent agreement with the results of the electron microprobe analysis. Details of the refinement and the comparison to that of de Villiers et al. (2009) are given in Table 1. A cif containing detailed information about data collection and structural refinement is supplied separately.

HEAT CAPACITY

Heat capacity measurements were carried out in a Quantum Design PPMS. The 9.1 mg sample was fixed to the measurement platform of the heat capacity puck with Apiezon N grease. The puck (plus grease) was measured through the temperature interval 2–300 K with and without the sample to determine the background contribution needed to obtain the heat capacity of the sample alone. At low temperatures, the heat capacity of the sample was larger than the background, but at temperatures above ~30 K, the background was larger.

Figure 3a shows a peak in the heat capacity of the crystal near 155 K. Broad features at 215 and 280 K are artifacts due to the Apiezon grease. A closer view of the peak (Fig. 3b) reveals it to be at 154 K with an apparent onset temperature of ~147 K and a tail up to ~157 K. Repeat measurements in a field of 9 T applied parallel to the [100] direction of the crystal ($H//a$ of the NiAs cell) yielded a peak at 148 K (Fig. 3b). The shape of the peak

TABLE 1. Crystal data and structure refinement details for 5C pyrrhotite

	This work	de Villiers et al. (2009)
Empirical formula	$\text{Fe}_{9.22(1)}\text{S}_{10}$	$\text{Fe}_{8.79}\text{Ni}_{0.118}\text{S}_{10}$
Formula weight	6682.51	6588.86
Temperature (°K)	293(2)	293(2)
Wavelength (Å)	0.71073	0.71073
Space group	<i>Cmce</i> (formerly <i>Cmca</i>)	<i>Cmce</i> (formerly <i>Cmca</i>)
Unit-cell dimensions	$a = 6.890(2) \text{ \AA}$ $b = 11.9436(4) \text{ \AA}$ $c = 28.7916(10) \text{ \AA}$ $\alpha = 90^\circ$ $\beta = 90^\circ$ $\gamma = 90^\circ$	$a = 6.893(3) \text{ \AA}$ $b = 11.939(3) \text{ \AA}$ $c = 28.635(15) \text{ \AA}$ $\alpha = 90^\circ$ $\beta = 90^\circ$ $\gamma = 90^\circ$
Volume	$2371.36(13) \text{ \AA}^3$	$2356.4(15) \text{ \AA}^3$
Z, Calculated density	8, 4.689 g/cm ³	8, 4.643 g/cm ³
Absorption coefficient	12.681	12.516
F_{000}	3358	3154
Crystal size	$0.08 \times 0.04 \times 0.02 \text{ mm}^3$	$0.14 \times 0.06 \times 0.03 \text{ mm}^3$
θ range for data collection	$2.12\text{--}31.82^\circ$	$2.85\text{--}26.34^\circ$
Limiting indices	$-9 \leq h \leq 9, -16 \leq k \leq 15, -40 \leq l \leq 42$	$-8 \leq h \leq 7, -8 \leq k \leq 14, -33 \leq l \leq 29$
Reflections collected/unique	29278/2084 ($R_{\text{int}} = 0.0322$)	6041/1264 ($R_{\text{int}} = 0.0322$)
Completeness to $\theta = 25.00$	99.7%	99.2%
Refinement method	Full-matrix least-squares on F^2	Full-matrix least-squares on F^2
Data/restraints/parameters	2084/1/120	1264/0/109
Goodness-of-fit on F^2	1.477	1.225
Final R indices [$I > 2\sigma(I)$]	$R1 = 0.0485, wR2 = 0.3231$	$R1 = 0.0716, wR2 = 0.1513$
R indices (all data)	$R1 = 0.0604, wR2 = 0.3431$	$R1 = 0.0937, wR2 = 0.1627$
Extinctions coefficient	—	0.00003(2)
Largest diff. peak and deepest hole	1.445 and $-1.346 \text{ e}^-/\text{\AA}^3$	1.533 and $-2.125 \text{ e}^-/\text{\AA}^3$

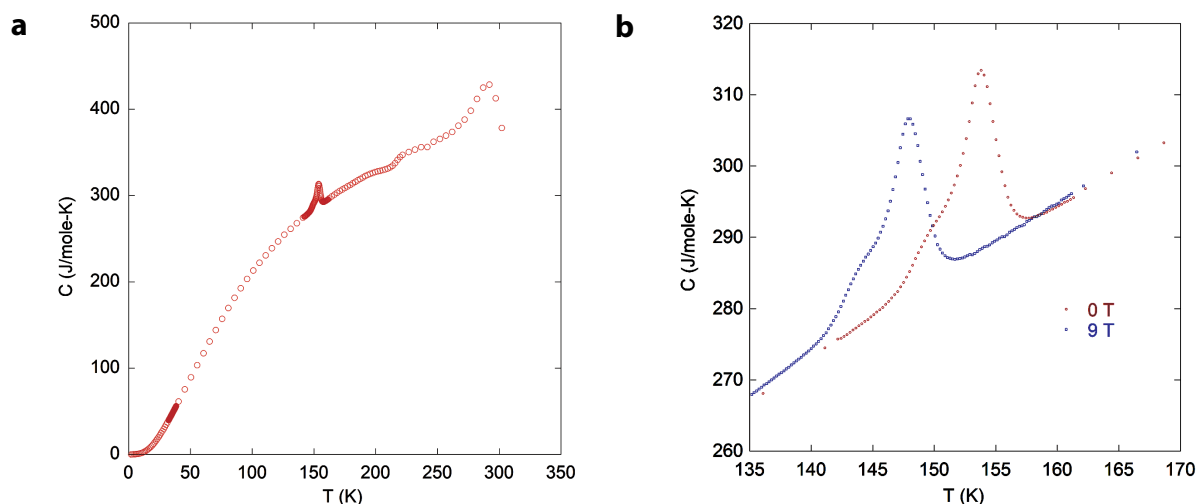


FIGURE 3. (a) Heat capacity of 5C crystal measured between 2 and 300 K in zero field, showing the magnetic transition near 155 K. Anomalies at ~215 and ~280 K are artifacts. (b) Higher resolution view of the peak at 154 K in zero field, which shifts to 148 K when measured in a 9 T field ($H//a$). (Color online.)

was unchanged, but the transition had clearly been shifted down in temperature by ~6 K. There is no evidence in the data for the Besnus transition at 35 K, which confirms that the crystal had fully transformed from the 4C structure. The peak is asymmetric. There is a shoulder on the low-temperature side suggesting that there are two contributions to the peak. This is somewhat similar to the heat capacity anomaly recently observed in 4C pyrrhotite (Haines et al. 2020b).

MAGNETIZATION

Magnetization was measured using a Quantum Design MPMS. Zero field cooled (ZFC) data were collected by cooling the crystal in zero applied field to 2 K before applying a 10 mT field ($H//a$) and measuring the moment in a continuous heating sweep up to 300 K at 3 K/min. Field cooled (FC) data were collected by cooling the crystal to 2 K in an applied field of 5 T before removing the 5 T field and applying a 10 mT field ($H//a$) during measurements of the moment in a continuous heating sweep up to 300 K at 3 K/min. There are two distinct features observable in both the ZFC and FC magnetization curves, at ~120 and ~155 K. The feature at ~155 K cannot be explained by any obvious impurity and matches up well with the transition seen in the heat capacity of the 5C crystal. The feature at ~120 K is almost certainly from the Verwey transition of magnetite, revealing the presence of a small amount of magnetite as an impurity phase. This is most likely remaining from incomplete removal of the thin oxidized layer, following the heat treatment at 875 K. The same crystal was used for both magnetization and heat capacity measurements, and the lack of any anomalies in the heat capacity at ~120 K supports the conclusion that the proportion of magnetite was very small.

To put the absolute values of magnetization in context, results for the 5C crystal and for a 4C crystal cut from the parent crystal temperature are compared in Figure 4b. 4C pyrrhotite is ferrimagnetic, due to an uncompensated moment arising from the fact that one in eight Fe sites is vacant. The measured moment of the 4C crystal at room temperature is a factor of ~100 larger

than that of the 5C crystal, suggesting that the magnetic ground state of 5C pyrrhotite is a fully compensated antiferromagnet. Furthermore, this puts an upper limit on the amount of 4C pyrrhotite remaining in the sample of approximately 1%. In the ZFC data, the step-like feature at 155 K takes place between 148 K and 155 K, with a midpoint of 152 K. The start-stop and mid-points of the step in the FC data are the same, although there is a small kink at the mid-point that is not observed in the ZFC data.

Figure 5a contains hysteresis (M - H) loops measured between +7 and -7 T at two temperatures well above and two temperatures well below the magnetic transition. The values of M never exceed ~2 Am²/kg and are smaller at all fields by a factor of at least 10 in comparison with the 4C structure (Powell et al. 2004; Charilaou et al. 2015). They also show no indication of saturation at any temperature, consistent with antiferromagnetic structures. Above the transition, the magnetization at 7 T (1.8 Am²/kg) is more than four times larger than it is below the transition (0.4 Am²/kg) at the same field. Below 150 K, [100] is a relatively hard direction, but becomes relatively soft above ~150 K. The difference remains marked even at 140 and 160 K, but there is a metamagnetic transition at 150 K from the low-temperature magnetic structure, at low fields, to the high-temperature structure at high fields (Fig. 5b). This is permissive of a first-order spin-flop transition between two antiferromagnetic structures that have their moments aligned in the plane perpendicular to the c -axis above the transition point and parallel to the c -axis below it. In this scenario, small openings of the curves at low fields (Fig. 5c) and the small hysteresis seen in the magnetization curves at all temperatures are attributed to the magnetite impurity identified on the basis of the magnetic anomaly at ~120 K (Fig. 3a). In addition, the (near) saturation moment of these two impurities (at a field of 1.5 T) would limit their presence in the sample to similar values. If the entire signal at 300 K and 1.5 T were attributed to magnetite (this is around 0.5 Am²/kg) this would equate to 46 μ g of magnetite or 0.5% of the total mass, using a value of 90 Am²/kg for saturation magnetization of magnetite (Hunt et al. 1995 and references therein). In a similar way, we

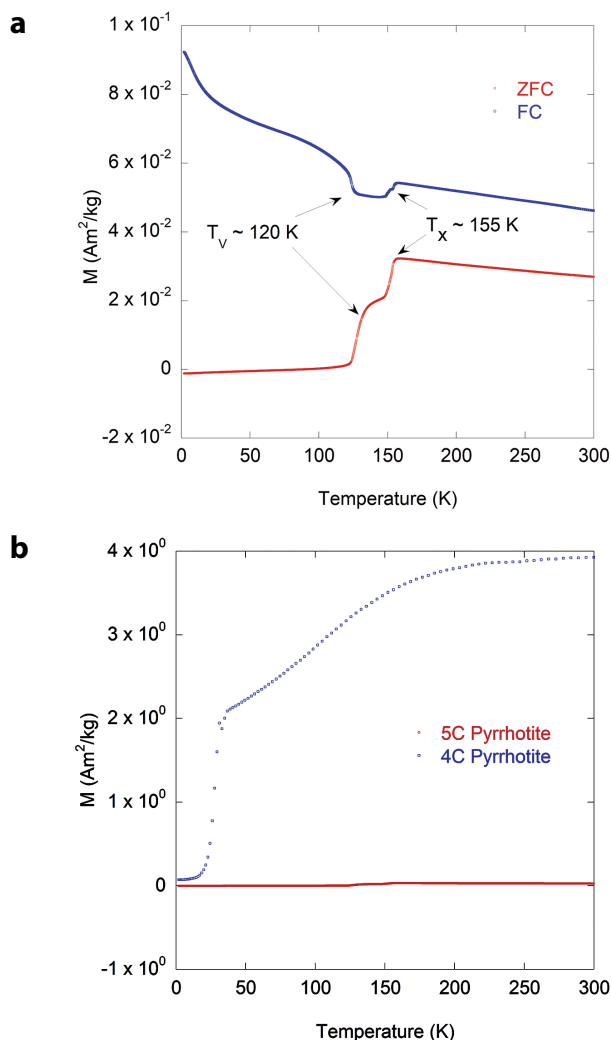


FIGURE 4. Magnetization, M , of 5C crystal. (a) ZFC and FC data, measured in a field of 10 mT ($H//a$). The anomaly at ~ 120 K is due to the presence of a small amount of magnetite (labeled as T_V for the Verwey transition) as impurity phase. The previously unknown transition is labeled as T_X . (b) Comparison with ZFC data for 4C and 5C crystals ($H//a$), showing a difference in magnetization of a factor of ~ 100 . (Color online.)

can constrain the 4C pyrrhotite to be less than 2.5% of the total mass (using $20 \text{ Am}^2/\text{kg}$ as the value of the magnetization from Hunt et al. (1995) and Haines et al. (2020b)).

RESONANT ULTRASOUND SPECTROSCOPY

Details of the instrument used to collect RUS data at low temperatures have been given elsewhere (McKnight et al. 2007). The sample sits lightly between two piezoelectric transducers in the RUS head, which is attached to the end of a stick and lowered into an Orange helium flow cryostat. In the present study, resonance spectra were collected in two automated cooling and heating sequences with steps of 30 K on cooling from room temperature to 10 K, and of between 1 and 10 K on heating from 10 to 295 K. A settle time of 1200 s was included

to allow for thermal equilibration at each set point. Individual spectra contained 65 000 data points in the frequency range 100 kHz to 2 MHz, with a driving voltage of 25 V. One sequence was for a different piece of the original large 4C crystal and the second was for the 9.1 mg fragment of the 5C crystal. Analysis of elastic and anelastic properties was undertaken by fitting selected peaks with an asymmetric Lorentzian function to give peak frequency, f , and width at half-maximum height, Δf . The natural resonances of a millimeter-sized sample involve primarily shearing motions and the variations of f^2 , therefore, reflect variations of different combinations of predominantly shear elastic constants, in this case of the single crystal. Acoustic dissipation is expressed in terms of the inverse mechanical quality factor, Q^{-1} , which, in a RUS experiment is usually specified as $\Delta f/f$.

Figure 6 contains a stack of spectra from the heating sequence of the 5C crystal. The y-axis is amplitude, but the spectra have been offset in proportion to the temperatures at which they were collected. The axis has then been relabeled as temperature to allow ready visualization of the principal features of the elastic behavior. All the resonances show the same pattern of reducing frequency (elastic softening) as the transition point is approached from above, followed by abrupt increases (elastic stiffening) at the expected transition temperature of ~ 155 K. In other words, all the shear elastic constants of the crystal evolve in more or less the same manner. Blue curves are fits to individual peaks, and Figure 7a shows the variations of f^2 and Q^{-1} for a peak near 650 kHz. With falling temperature there is a trend of elastic softening by a few percents toward the transition point, followed by $\sim 10\%$ stiffening in a narrow temperature interval between 150 and 160 K. This temperature interval corresponds almost exactly with the temperature interval over which the anomaly in heat capacity extends (Fig. 3). The peaks generally remain quite sharp at all temperatures, with values of Q^{-1} in the vicinity of 2×10^{-3} apart perhaps from a slight increase in the vicinity of the transition point. The variation of f^2 normalized to the room-temperature value for three different peaks is shown in Figure 7b. While the overall temperature dependence is similar the peaks behave slightly differently, as would be expected for a single-crystal sample in which each resonance has a distinct contribution from the different elastic constants.

Variations of f^2 and Q^{-1} data from fits to a resonance peak near 620 kHz in spectra collected from the piece of original the 4C crystal are shown in Figure 7c. The crystal was cut from the same original sample as the piece that was converted to 5C. There are very obvious differences from the variations in elastic and anelastic properties that accompany the magnetic transition shown in Figure 7. In particular, softening by a few percents with falling temperature is associated with a peak in Q^{-1} at ~ 270 K. This turns into a trend of gradual stiffening followed by steep softening ahead of the Besnus transition, which is marked by a minimum at ~ 36 K. f^2 values then recover steeply and there is a distinct peak in Q^{-1} immediately below the transition. The maximum change in f^2 at the frequency of this resonance, ~ 620 kHz, is $\sim 6\%$. Changes in elastic and anelastic properties accompanying the Besnus transition in 4C pyrrhotite are described in detail elsewhere (Haines et al. 2020b).

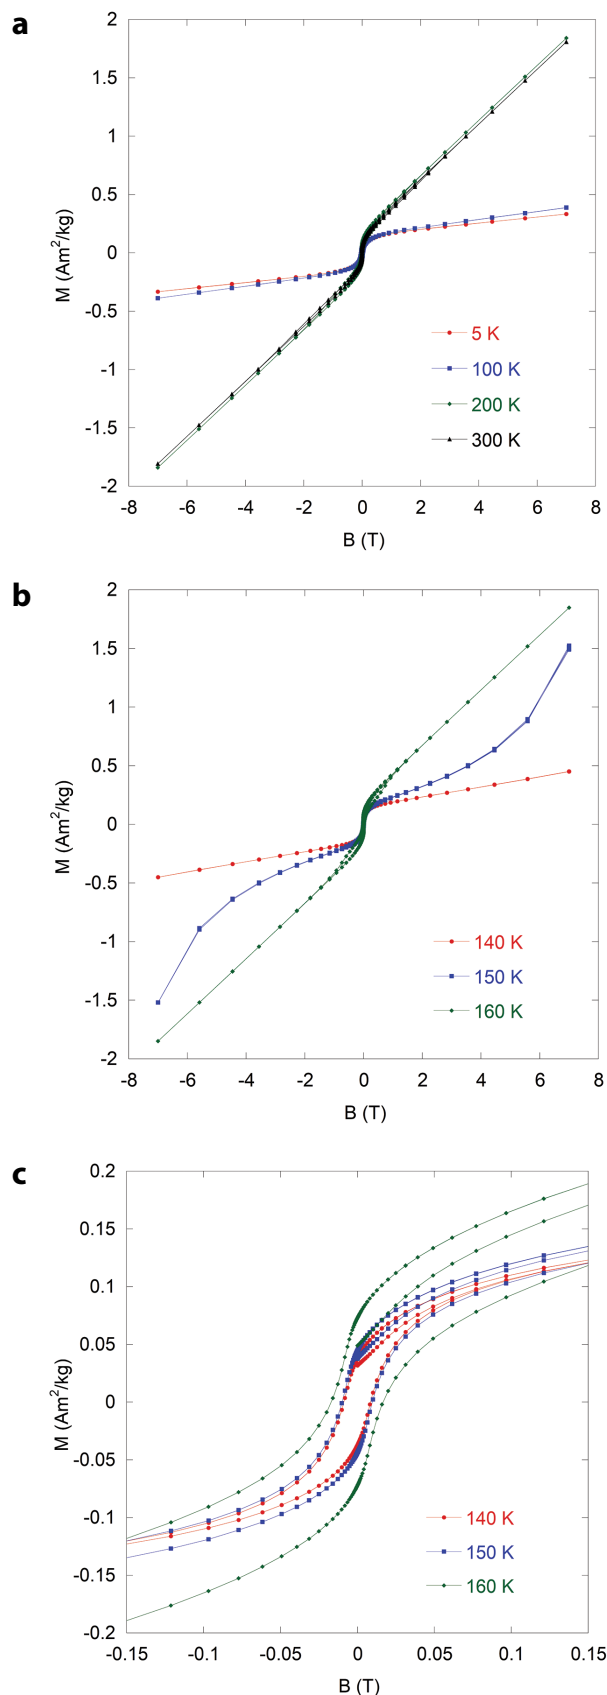


FIGURE 5. (a) Field and temperature dependence of the magnetization of the 5C sample. The field was applied parallel to the [100] direction of the parent NiAs structure unit cell ($H//a$). The structure at 200 and 300 K has marked differences in magnetic anisotropy from the structure at 5 and 100 K. Neither show any indication of saturation at high fields. (b) Field and temperature dependence of magnetization of the 5C structure close to the magnetic transition at ~ 155 K ($H//a$). (c) Close in view of the low field region from b, showing slight opening of the loops that is attributed to the presence of a small amount of magnetite. (Color online.)

DISCUSSION AND CONCLUSIONS

We have shown that 4C pyrrhotite can be transformed to 5C by annealing above the concomitant Néel and vacancy ordering temperature. On the basis of single-crystal X-ray diffraction at room temperature we confirm that a model in space group $Cmce$ can successfully explain the diffraction data. The low-temperature structure has previously been refined successfully using a model in space group $P2_1$ by Liles and De Villiers (2012). The Besnus transition is no longer observed and a new Morin-like spin-flop transition occurs at ~ 155 K instead. The magnetic properties of the 5C crystal are incompatible with impurities of 4C pyrrhotite or magnetite above the level of 1%. In addition, the heat capacity anomalies characteristic of the low-temperature magnetic phase transitions in these two minerals were not observed. The 4C crystal from which the piece used in this study was cut showed no impurities above the level of detection in either powder XRD or electron microprobe measurements (Haines et al. 2020a). Therefore, it is difficult to imagine any impurity other than the magnetite formed at the surface or “untransformed” 4C pyrrhotite. We have carried out electron microprobe analysis on the 5C crystal and the sample is monophase with a high degree of homogeneity. The impurity levels are on the border of detectability. The stoichiometry is homogeneous and works out to be $\text{Fe}_{9.2}\text{S}_{10}$ in good agreement with the single-crystal refinement.

The most significant structural difference in comparison with the 4C structure is the change in vacancy ordering scheme

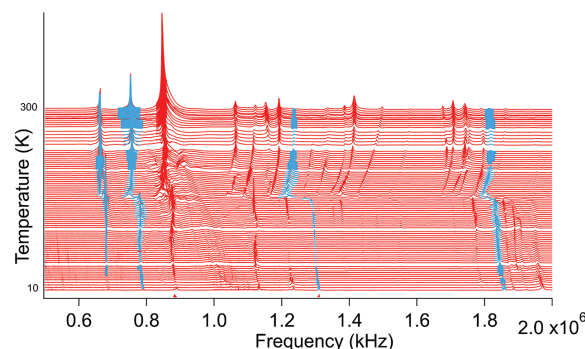


FIGURE 6. RUS spectra collected from the 9.1 mg piece of the 5C crystal in a heating sequence from 10 to 295 K. The y-axis should be amplitude in volts, but the spectra have been offset in proportion to the temperatures at which they were collected and the axis relabeled as temperature. There is an abrupt change in frequencies of all the individual resonance peaks at the expected transition temperature, ~ 155 K. Fits to selected peaks are shown in blue. (Color online.)

that develops during cooling. Without specifying the ordering in detail, it is possible to assess the changes in structure and properties from the perspective of symmetry. If the reference structure at high temperatures is taken to be that of NiAs in space group $P6_3/mmc$, the order parameter that gives rise to the 5C superstructure is most likely to have the symmetry of the active representation $U1(\frac{1}{2}, 0, \frac{1}{2})$ (Haines et al. 2019). A likely candidate for the magnetic order parameter has the symmetry of irreducible representation $m\Gamma_5^-$. The list of possible magnetic space groups that can result from this combination includes the

previously reported crystallographic space groups $Cmce$, $P2_1/c$, and $P2_1$ (Haines et al. 2019). New magnetic and elasticity data have been interpreted here on the basis that 5C pyrrhotite is antiferromagnetic and that the magnetic transition at ~155 K is from one antiferromagnetic structure to another. In all of the reported space groups, the moments can be aligned either in the plane perpendicular to the crystallographic c -axis of the parent or parallel to the c -axis. Across the $Fe_{1-x}S$ phase diagram (Schwarz and Vaughan 1972) the 590 K transition is to a state in which the moments are in the plane perpendicular to the crystallographic c -axis. The low-temperature spin-flop transition observed in troilite, and the low-temperature evolution of 4C pyrrhotite involves a rotation of the moments toward the c -axis.

Haines et al. (2019) predicted that the magnetic transition in 5C would be an abrupt spin-flop transition. This is because for none of the experimentally reported structures is it possible to have distortions that allow both $m\Gamma_4^+$ and $m\Gamma_5^+$ to have non-zero values. In other words, the moments are strictly confined to either the plane perpendicular to the c -axis or to the direction parallel to the c -axis. $Cmce$ was reported for a crystal at room temperature with the $P2_1$ structure being solved using data collected at 120 K. These two structures do not have a group-subgroup relationship so that a $Cmce$ – $P2_1$ transition is necessarily first order.

The spin-flop transition in 5C pyrrhotite is significantly different from the Besnus transition in 4C pyrrhotite, as is seen clearly in differences between the two sets of elastic and anelastic data in Figure 7. As a function of temperature, the spin-flop transition is characterized by a steep increase in all the shear elastic constants over a narrow temperature interval, consistent with first-order character. The low-temperature structure is stiffer than the high-temperature structure and has the same level of acoustic loss. In contrast, the Besnus transition occurs over a wider temperature interval, consistent with a second-order transition between magnetic structures that do have a group-subgroup relationship. There is also a distinct peak in the acoustic loss that could relate to the development of a ferroelastic microstructure. Thus, the transition in the 5C crystal appears to be closely analogous to the magnetic transition to that seen in FeS at 440 K, which involves the same change in orientation of moments (Hirahara and Murakami 1958; Andresen et al. 1960, 1967; Sparks et al. 1960, 1962; Horwood et al. 1976).

This combination of symmetry analysis and experimental data on the magnetoelastic behavior shows that 5C pyrrhotite fits well into the wider picture for the diverse structures suggested for the system $Fe_{1-x}S$ by Haines et al. (2019). The stable antiferromagnetic/ferrimagnetic structure that appears across the solid solution at ~590 K has moments aligned perpendicular to the crystallographic c -axis. At transition temperatures that reduce from ~440 K with increasing concentration of vacancies, this gives way to another magnetic structure in which the preferred orientation of the moments is 90° away from the c -axis. Details of the precise magnetic structure and possibilities for thermodynamically continuous pathways between the two magnetic states then depend on details of the vacancy ordering at different stoichiometries, as expressed in terms of order parameters with irreducible representations of the form $U(\frac{1}{2}, 0, \frac{1}{x})$ where x is 3, 4, 5, 6 or irrational, corresponding to the 3C, 4C, 5C, 6C, and incommensurate phases of pyrrhotite. All these phases, apart

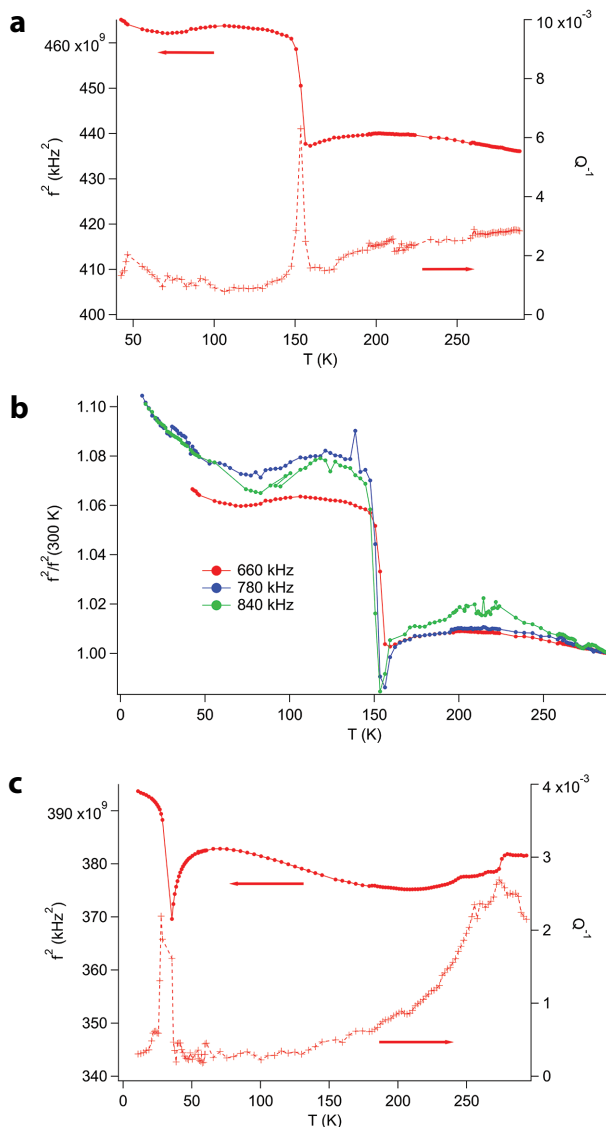


FIGURE 7. (a) Temperature dependence of f^2 and Q^{-1} for the single crystal of 5C pyrrhotite from fitting of the resonance peak near 650 kHz and (b) f^2 for three resonance peaks at 660, 780, and 840 kHz normalized to the value at room temperature. (c) Temperature dependence of f^2 and Q^{-1} for a single resonance with frequency near 620 kHz from a 4C pyrrhotite crystal cut from the same original sample as was used to produce the 5C crystal. The Besnus transition is marked by a minimum of f^2 at ~36 K. Crosses = Q^{-1} , right axis; filled circles = f^2 , left axis. (Color online.)

from 3C, are expected to show one magnetic transition below room temperature. In 3C pyrrhotite, the transition is expected to be above room temperature.

IMPLICATIONS

The discovery of a low-temperature spin-flop transition in the 5C superstructure of pyrrhotite must be seen within the context of the whole Fe_{1-x}S family. In this work, we have shown that the behavior of the 5C superstructure is consistent with a comprehensive group theoretical framework described in Haines et al. (2019). The result fits with the 3C superstructure being ferrimagnetic at room temperature and, if the crystallographic space group of $P3_121$ (Nakano et al. 1979; Keller-Besrest et al. 1983) is correct, with the magnetic moments aligned parallel to the c -axis. A low-temperature spin-reorientation transition like the Besnus transition must also be expected in the 6C superstructure. Thus, it seems that the spin flop transitions are all closely related and fundamentally due to the same underlying thermodynamic driving force.

An additional consideration relates to the fact that the 5C crystal studied in this work was the result of thermally cycling a 4C crystal through the concomitant vacancy ordering and ferrimagnetic ordering temperature, at 595 K, and then up to 875 K before cooling back to room temperature. To our knowledge, this is the first time that 5C pyrrhotite has been synthesized in this way.

Finally, our improved understanding of the nature of the vacancy ordering and related magnetic structures in the Fe_{1-x}S system means that an understanding of the microscopic mechanisms may now be within reach for an important group of mineral sulfides. Further experiments and calculations should focus on the changes in the electronic structure behind the changing magnetic anisotropy and its dependence on temperature, pressure, and vacancy order.

FUNDING

The authors acknowledge funding from the Leverhulme Foundation, grant number RPG2016-298. Heat capacity and DC magnetic measurements were carried out using the Advanced Materials Characterization Suite, funded by EPSRC Strategic Equipment Grant EP/M000524/1. RUS facilities in Cambridge were funded by grants to MAC from the Natural Environment Research Council of Great Britain (grant nos. NE/B505738/1 and NE/F17081/1) and from the Engineering and Physical Sciences Research Council (grant no. EP/I036079/1).

REFERENCES CITED

- Andresen, A.F., Hofman-Bang, N., Bak, T.A., Varde, E., and Westin, G. (1960) Magnetic phase transitions in stoichiometric FeS studied by means of neutron diffraction. *Acta Chemica Scandinavica*, 14, 919–926.
- Andresen, A.F., Torbo, P., Ostlund, E., Bloom, G., and Hagen, G. (1967) Phase transitions in Fe_xS ($x = 0.90$ – 1.00) studied by neutron diffraction. *Acta Chemica Scandinavica*, 21, 2841–2848.
- Bertaut, E.F. (1953) Contribution à l'étude des structures lacunaires: la pyrrhotine. *Acta Crystallographica*, 6, 557–561.
- Besnus, M.J., and Meyer, A.J.P. (1964) Nouvelles données expérimentales sur le magnétisme de la pyrrhotine naturelle. Proceedings of the International Conference on Magnetism, Nottingham, September 1964, 507–511.
- Charilaou, M., Kind, J., Koulialias, D., Weidler, P.G., Mensing, C., Löffler, J.F., and Gehring, A.U. (2015) Magneto-electronic coupling in modulated defect-structures of natural Fe_{1-x}S . *Journal of Applied Physics*, 118, 83903.
- de Villiers, J.P.R., and Liles, D.C. (2010) The crystal-structure and vacancy distribution in 6C pyrrhotite. *American Mineralogist*, 95, 148–152.
- de Villiers, J.P.R., Liles, D.C., and Becker, M. (2009) The crystal structure of a naturally occurring 5C pyrrhotite from Sudbury, its chemistry, and vacancy distribution. *American Mineralogist*, 94, 1405.
- Elliot, A.D. (2010) Structure of pyrrhotite 5C (Fe_8S_{10}). *Acta Crystallographica*, B66, 271–279.
- Fleet, M.E. (1971) The crystal structure of a pyrrhotite (Fe_7S_8). *Acta Crystallographica*, B27, 1864–1867.
- Haines, C.R.S., Howard, C.J., Harrison, R.J., and Carpenter, M.A. (2019) Group-theoretical analysis of structural instability, vacancy ordering and magnetic transitions in the system troilite (FeS)–pyrrhotite (Fe_{1-x}S). *Acta Crystallographica*, B75, 1208–1224.
- Haines, C.R.S., Lampronti, G.I., and Carpenter, M.A. (2020a) Magnetoelastic coupling associated with vacancy ordering and ferrimagnetism in natural pyrrhotite, Fe_7S_8 . *Journal of Physics: Condensed Matter*, 32, 385401.
- Haines, C.R.S., Dutton, S.E., Volk, M.W.R., and Carpenter, M.A. (2020b) Order parameter coupling and microstructure dynamics at the Besnus transition in 4C pyrrhotite, Fe_7S_8 . *Journal of Physics: Condensed Matter*, 32, 405401.
- Hirahara, E., and Murakami, M. (1958) Magnetic and electrical anisotropies of iron sulfide single crystals. *Journal of Physics and Chemistry of Solids*, 7, 281–289.
- Horwood, J.L., Townsend, M.G., and Webster, A.H. (1976) Magnetic susceptibility of single-crystal Fe_{1-x}S . *Journal of Solid State Chemistry*, 17, 35–42.
- Hunt, C.P., Moskowitz, B.M., and Banerjee, S.K. (1995) Magnetic Properties of Rocks and Minerals. In T.J. Ahrens, Ed., *Handbook of Physical Constants*, vol. 3, pp. 189–204. American Geophysical Union.
- Izaola, Z., González, S., Elcoro, L., Perez-Mato, J.M., Madariaga, G., and García, A. (2007) Revision of pyrrhotite structures within a common superspace model. *Acta Crystallographica*, B63, 693–702.
- Keller-Besrest, F., Collin, G., and Comes, R. (1983) Structure and planar faults in the defective NiAs-type compound 3C Fe_7S_8 . *Acta Crystallographica*, B39, 296–303.
- Kontny, A., de Wall, H., Sharp, T.G., and Pösfai, M. (2000) Mineralogy and magnetic behavior of pyrrhotite from a 260 °C section at the KTB drilling site, Germany. *American Mineralogist*, 85, 1416.
- Koto, K., Morimoto, N., and Gyobu, A. (1975) The superstructure of the intermediate pyrrhotite. I. Partially disordered distribution of metal vacancy in the 6 C type, $\text{Fe}_{11}\text{S}_{12}$. *Acta Crystallographica*, B31, 2759–2764.
- Liles, D.C., and De Villiers, J.P.R. (2012) Redetermination of the structure of 5C pyrrhotite at low temperature and at room temperature. *American Mineralogist*, 97, 257–261.
- Martin-Hernández, F., Dekkers, M.J., Bominaar-Silkens, I.M.A., and Maan, J.C. (2008) Magnetic anisotropy behaviour of pyrrhotite as determined by low- and high-field experiments. *Geophysical Journal International*, 174, 42–54.
- McKnight, R.E.A., Carpenter, M.A., Darling, T.W., Buckley, A., and Taylor, P.A. (2007) Acoustic dissipation associated with phase transitions in lawsonite, $\text{CaAl}_2\text{Si}_2\text{O}_7 \cdot (\text{OH})_2 \cdot \text{H}_2\text{O}$. *American Mineralogist*, 92, 1665–1672.
- Morimoto, N., Gyobu, A., Tsukama, K., and Koto, K. (1975) Superstructure and non-stoichiometry of intermediate pyrrhotite. *American Mineralogist*, 60, 240–248.
- Nakano, A., Tokonami, M., and Morimoto, N. (1979) Refinement of 3C pyrrhotite, Fe_7S_8 . *Acta Crystallographica*, B35, 722–724.
- Nakazawa, H., and Morimoto, N. (1971) Phase relations and superstructures of pyrrhotite, Fe_{1-x}S . *Materials Research Bulletin*, 6, 345–358.
- Pösfai, M., Sharp, T.G., and Kontny, A. (2000) Pyrrhotite varieties from the 9.1 km deep borehole of the KTB project. *American Mineralogist*, 85, 1406.
- Powell, A. V., Vaquero, P., Knight, K.S., Chapon, L.C., and Sanchez, R.D. (2004) Structure and magnetism in synthetic pyrrhotite Fe_7S_8 : A powder neutron-diffraction study. *Physical Review B*, 70.
- Rigaku Oxford Diffraction (2018) CrysAlisPro Software System.
- Rochette, P., Gattacceca, J., Chevrier, V., Hoffmann, V., Lorand, J.-P., Funaki, M., and Hochleitner, R. (2005) Matching Martian crustal magnetization and magnetic properties of Martian meteorites. *Meteoritics and Planetary Science*, 40, 529–540.
- Schwarz, E.J., and Vaughan, D.J. (1972) Magnetic phase relations of pyrrhotite. *Journal of Geomagnetism and Geoelectricity*, 24, 441–458.
- Sheldrick, G.M. (1997) SHELXS-97 and SHELXL-97, Program for Crystal Structure Solution and Refinement. University of Göttingen, Germany.
- Sparks, J.T., Mead, W., Kirschbaum, A.J., and Marshall, W. (1960) Neutron diffraction investigation of the Fe_{1-x}S system. *Journal of Applied Physics*, 31, S356–S357.
- Sparks, J.T., Mead, W., and Komoto, T. (1962) Neutron diffraction investigation of the magnetic and structural properties of near-stoichiometric iron sulfide. *Journal of the Physical Society of Japan*, 17(Suppl.), 249–252.
- Yamamoto, A., and Nakazawa, H. (1982) Modulated structure of the NC-type ($N = 5.5$) pyrrhotite, Fe_{1-x}S . *Acta Crystallographica Section A*, 38, 79–86.

MANUSCRIPT RECEIVED AUGUST 20, 2019

MANUSCRIPT ACCEPTED FEBRUARY 26, 2020

MANUSCRIPT HANDLED BY OLIVER TSCHAUNER

Endnote:

¹Deposit item AM-20-97266, CIF and Supplemental Material. Deposit items are free to all readers and found on the MSA website, via the specific issue's Table of Contents (go to http://www.minsocam.org/MSA/AmMin/TOC/2020/Sep2020_data/Sep2020_data.html).